

AD-A066 972

ALABAMA UNIV UNIVERSITY DEPT OF CHEMISTRY

F/G 11/9

SYNTHESIS OF POLYESTERS CONTAINING TETRATHIAFULVALENE GROUPS IN--ETC(U)

MAR 79 C U PITTMAN, Y LIANG, M UEDA

N00014-75-C-0689


UNCLASSIFIED

TR-23(ONR)

NL


| OF |

AD  
A066972



END  
DATE  
FILMED  
6-79

DDC

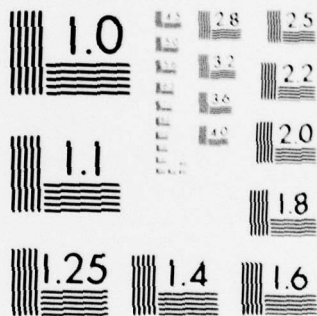

MICROCOPY RESOLUTION TEST CHART  
NATIONAL BUREAU OF STANDARDS-1963-A

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

| 14 REPORT DOCUMENTATION PAGE  |  | 12 READ INSTRUCTIONS<br>BEFORE COMPLETING FORM   |
|---|--|--|
| 1. REPORT NUMBER<br>ONR-TR-23 (ONR)   | 2. GOVT ACCESSION NO.  | 3. RECIPIENT'S CATALOG NUMBER  |
| 4. TITLE (and Subtitle)<br>Synthesis of Polyesters Containing<br>Tetrathiafulvalene Groups in the Backbone  | 5. TYPE OF REPORT & PERIOD COVERED<br>Interim Technical Report |  |
| 6. PERFORMING ORG. REPORT NUMBER  |  | 7. CONTRACT OR GRANT NUMBER(s)<br>N00014-75-C-0689   |
| 8. AUTHOR(s)<br>Charles U. Pittman, Jr., Yeon-Fong Liang and Mitsuru Ueda   |  | 9. PERFORMING ORGANIZATION NAME AND ADDRESS<br>Department of Chemistry, University of Alabama<br>University, Alabama 35486 |
| 10. CONTROLLING OFFICE NAME AND ADDRESS<br>Department of the Navy<br>Office of Naval Research<br>Arlington, Virginia 22217  |  | 11. PROGRAM ELEMENT, PROJECT, TASK<br>AREA & WORK UNIT NUMBERS<br>NR-356-561   |
| 12. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)   |  | 13. REPORT DATE<br>March 5, 1979   |
| 14. SECURITY CLASS. (of this report)<br>Unclassified  |  | 15. NUMBER OF PAGES<br>18  |
| 16. DISTRIBUTION STATEMENT (of this Report)<br>Approved for public release, distribution unlimited. Reproduction is<br>permitted for any purpose of the United States Government.   |  | 17. SECURITY CLASS. (of this report)<br>Unclassified   |
| 18. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)<br>Distribution of this document is unlimited.   |  | 19. DECLASSIFICATION/DOWNGRADING<br>SCHEDULE   |
| 16. DISTRIBUTION STATEMENT (of this Report)<br>Approved for public release, distribution unlimited. Reproduction is<br>permitted for any purpose of the United States Government.   |  |  |
| 17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)<br>Distribution of this document is unlimited.   |  |  |
| 18. SUPPLEMENTARY NOTES<br>This paper is accepted for publication in <u>Macromolecules</u> in 1979.   |  |  |
| 19. KEY WORDS (Continue on reverse side if necessary and identify by block number)<br>polyesters, tetrathiafulvalene, polycondensation, tetracyanoquinodimethane,<br>bromine complexes, semiconductors, 2,6(7)-bis(p-hydroxyphenyl)tetrathiaful-<br>valene, diacid chlorides.   |  |  |
| 20. ABSTRACT (Continue on reverse side if necessary and identify by block number)<br>New polyesters, incorporating the tetrathiafulvalene (TTF) moiety within the<br>polymer backbone, were prepared by polycondensation of 2,6(7)-bis(p-hydroxyphenyl)-<br>tetrathiafulvalene with either sebacyl chloride or terephthalyl chloride using<br>solution techniques. The effects of various bases, solvents, and reaction<br>temperatures were studied, but the molecular weights were rather low in all<br>cases. The polymers were highly soluble in CF <sub>3</sub> COOH, soluble in dipolar aprotic<br>solvents (i.e., HMPA, DMSO, DMF) on heating, slightly soluble in THF and acetone |  |  |

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 63 IS OBSOLETE  
S/N 0102-014-6601Unclassified March 5, 1979  
SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

AD A0 66972

DDC FILE COPY

406 969

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

20. ABSTRACT (continued)

and largely insoluble in other common solvents. TGA and DTA studies indicated the polyesters were stable to about 270° and an exotherm (in air) occurred at 280° followed by rapid weight loss. Attempts to prepare tetracyanoquinodimethane (TCNQ) or 2,3-dichloro-5,6-dicyanoquinone (DDQ) complexes were unsuccessful. Bromine complexes were prepared.

|                                 |   |
|---------------------------------|---|
| ACCESSION FOR                   |   |
| THIS                            | White Section <input checked="" type="checkbox"/> |
| DOE                             | B.M. Section <input type="checkbox"/>             |
| UNANNOUNCED                     | <input type="checkbox"/>                          |
| DISSEMINATION                   |   |
| BY                              |   |
| DISTRIBUTION/AVAILABILITY CODES |   |
| SPECIAL                         |   |
| A                               |   |

Unclassified

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)



SYNTHESIS OF POLYESTERS CONTAINING TETRATHIAFULVALENE  
GROUPS IN THE BACKBONE

Charles U. Pittman, Jr.,\* Yeon-Fong Liang, and Mitsuru Ueda  
Department of Chemistry, University of Alabama  
University (Tuscaloosa), Alabama 35486

ABSTRACT: New polyesters, incorporating the tetrathiafulvalene (TTF) moiety within the polymer backbone, were prepared by polycondensation of 2,6(7)-bis(p-hydroxyphenyl)tetrathiafulvalene with either sebacyl chloride or terephthalyl chloride using solution techniques. The effects of various bases, solvents, and reaction temperatures were studied, but the molecular weights were rather low in all cases. The polymers were highly soluble in  $\text{CF}_3\text{COOH}$ , soluble in dipolar aprotic solvents (i.e., HMPA, DMSO, DMF) on heating, slightly soluble in THF and acetone and largely insoluble in other common solvents. TGA and DTA studies indicated the polyesters were stable to about  $270^\circ$  and an exotherm (in air) occurred at  $280^\circ$  followed by rapid weight loss. Attempts to prepare tetracyanoquinodimethane (TCNQ) or 2,3-dichloro-5,6-dicyanoquinone (DDQ) complexes were unsuccessful. Bromine complexes were prepared.

## Introduction

2


Studies of highly conducting organic charge-transfer (CT) complexes have attracted enormous recent interest with the development of pseudo-one-dimensional organic metals.<sup>1,2</sup> In particular, molecular CT complexes of either tetrathiafulvalenes (TTF)<sup>3,4</sup> or tetraselenafulvalenes (TSeF)<sup>5,6</sup> with tetracyanoquinodimethane (TCNQ) have been most intensively investigated owing to their quasi-metallic conductivity. The preparation of TTF and TSeF derivatives have been reviewed<sup>7</sup> and new synthetic procedures for preparing unsymmetrical TTF derivatives continue to appear regularly.<sup>8-12</sup> However, there exists a clear need for such conductors with improved material properties and three dimensional conductivity. One approach to this problem is to prepare multidimensional networks<sup>21</sup> or polymers.

Many reports of semiconducting organic polymers have appeared.<sup>13</sup> One approach has been to make anion-radical TCNQ salts of polymeric cations.<sup>14,15</sup> Conductivities as high as  $\sim 10^{-2} \text{ ohm}^{-1} \text{ cm}^{-1}$  were obtained for TCNQ complexes of poly(3-vinylbisfulvalenediiron),<sup>16,17</sup> while TCNQ, DDQ, and  $\text{I}_3^-$  complexes of poly(vinylferrocene), poly(ferrocenylene), and poly(ethynylferrocene) had conductivities below  $10^{-5} \text{ ohm}^{-1} \text{ cm}^{-1}$ .<sup>17,18</sup> Polymers containing TTF units, however, have been much less studied owing, in part, to the relative logistics encountered in monomer synthesis.


Among the first TTF-containing polymers were those prepared via a polycoupling process by Okawara et al.<sup>19</sup> Only two reports of condensation polymers containing TTF exist; polyurethanes<sup>20</sup> and polyamides<sup>21</sup> were synthesized and both failed to form CT complexes with TCNQ and DDQ. Three vinyl monomers of TTF have now been made. Vinyltetrathiafulvalene, 1, gave low molecular weight polymers on standing or exposure to UV or azo initiators.<sup>22</sup> (p-Vinylphenyl)tetrathiafulvalene, 2, resisted anionic and radical initiation but thermally polymerized in bulk. Its polymer was insoluble and did not give TCNQ complexes, although bromine

79 04 02 015

complexes were reported.<sup>23</sup> Finally, acrylate **3** was prepared and both homo- and copolymerized. Its polymers gave evidence of TCNQ complexation.<sup>24</sup>

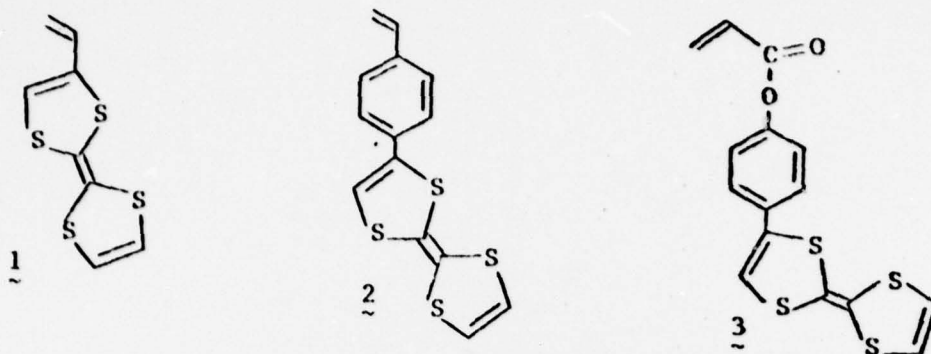

We now report the polycondensation of 2,6(7)-bis(*p*-hydroxyphenyl)tetra-thiafulvalene, **4**,<sup>25</sup> with diacid chlorides.

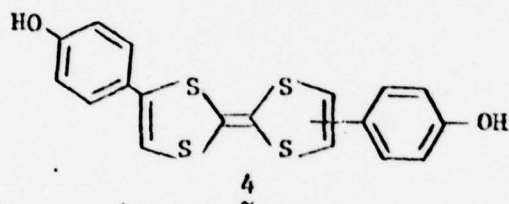

## Experimental Section

**Materials. Solvents and Nitrogen bases.** 1,2-Dichloroethane was purified by washing sequentially with diluted aqueous acid, water, diluted aqueous base, and water followed by drying (anhydrous Na<sub>2</sub>SO<sub>4</sub>) and distillation from calcium hydride. N,N-Dimethylacetamide (DMAc) and hexamethylphosphortriamide (HMPA) were distilled under nitrogen from phosphorus pentaoxide. Tetramethylene sulfone (TMS) was purified by warming over potassium permanganate, filtration, and distillation from phosphorus pentaoxide under vacuum. Chloroform was purified by aqueous washing, drying, and distillation from calcium hydride. Toluene and *p*-xylene were distilled from calcium hydride under nitrogen. Nitrobenzene was purified by aqueous washing, drying (CaH), and distillation from phosphorus pentaoxide at 1 atm. Triethylamine and N-ethylmorpholine were distilled from phosphorus pentaoxide under nitrogen while pyridine, 2-picoline, 2,6-lutidine, and isoquinoline were distilled from barium oxide

under nitrogen.

Monomers. Sebacyl chloride (Eastman Kodak) was distilled at reduced pressure under nitrogen. Terephthaloyl chloride (Aldrich Chem. Co.) was recrystallized from *n*-hexane. 2,6(7)-Bis(*p*-hydroxyphenyl)tetrathiafulvalene prepared according to our previously published eight step synthesis<sup>25</sup> starting with the 4-hydroxyacetophenone in 29% overall yield. However, monomer 4 was found to be unstable in the air and this required a modification of the last step as described below.

To a suspension of 2,6(7)-bis(*p*-acetoxyphenyl)tetrathiafulvalene (0.47 g, 1.0 mmol) in methanol (20 ml), hydrazine hydrate (3 ml) was added. The reaction was stirred at room temperature, while the color changed from orange to blood red. After 12h, deoxygenated water was added and a red precipitate was filtered under nitrogen. Recrystallization from nitrogenated pre-boiling methanol gave golden air sensitive crystals (which were stored in an inert atmosphere) melting at 207-208°C. Ir (KBr) 1600, 1548, 1502, 1455, 1382, 1248, 1172, 919, 825, 760  $\text{cm}^{-1}$ ; NMR (DMSO- $d_6$ )  $\delta$ 6.74-7.43 (multiplet, aromatic, 8H), 6.95 (s, 2, ring H), 3.42 (s, OH, 2H). Anal. Calcd for  $\text{C}_{18}\text{H}_{12}\text{S}_4\text{O}_2$ : C, 55.66; H, 3.09; S, 33.02. Found: C, 55.56; H, 3.10; S, 32.87.

Polymerization. 1. Low temperature solution polymerizations. Two methods were used as given below.

Method A. 2,6(7)-Bis(*p*-hydroxyphenyl)tetrathiafulvalene (0.3885 g, 1.0 mmol) was placed in a dried, 50 ml flask equipped with a magnetic stirrer and pressure-equalizing dropping funnel which was fitted with a drying tube filled with calcium chloride. Purified *N,N*-dimethylacetamide (1 ml) and purified pyridine (0.1584 g, 2 mmol) were added with a pipet into the flask and the mixture was cooled (ice bath) with stirring. Sebacyl chloride (0.2391 g, 1 mmol), in 1 ml of purified 1,2-dichloroethane, was added dropwise to the cooled diol solution followed by stirring at room temperature for 12h. The polymer was precipitated



by adding the reaction solution to 100 ml of water, collected by suction filtration, and washed thoroughly with water. After drying over phosphorus pentaoxide at 80°C (0.2 torr) for 48h, 0.50 g (90%) of polymer was obtained. The inherent viscosity in  $\text{CF}_3\text{COOH}$  was 0.14 measured at a concentration of 0.5 g/dl at 30°C.

Method B. 2,6(7)-Bis(p-hydroxyphenyl)tetrathiafulvalene (0.3885 g, 1 mmol) was placed in a dried 50 ml flask equipped with a magnetic stirring bar. N,N-Dimethylacetamide (DMAc), 1 ml, triethylamine (0.2024 g, 2 mmol) were added with stirring. A solution of sebacyl chloride (0.2391 g, 1 mmol), dissolved in 1 ml of purified N,N-dimethylacetamide (DMAc), was added all at once to the stirred diol suspension without cooling. After addition, the polymerization mixture was stirred at 20-25°C for 12h. Then water (100 ml) was added. The resulting polymer was filtered, washed thoroughly with water, and the brown solid product was dried over phosphorus pentaoxide at 80°C (0.2 torr) for 48h giving 0.54 g (98%). The inherent viscosity in  $\text{CF}_3\text{COOH}$  was 0.16 measured at a concentration of 0.5 g/dl at 30°C.

2. Typical higher temperature solution polymerization. 2,6(7)-Bis(p-hydroxyphenyl)tetrathiafulvalene (0.3885 g, 1 mmol) was placed in a dried, 50 ml, flask equipped with a magnetic stirrer and condenser. p-Xylene (1 ml) and pyridine (0.1584 g, 2 mmol) were added and the flask was heated under nitrogen. Sebacyl chloride (0.2391 g, 1 mmol), dissolved in 1 ml of p-xylene, was added all at once to the boiling diol suspension with vigorous stirring. The reaction was stirred at reflux for 12h. The polymer was obtained by precipitation from cold water (100 ml), filtration, water-washing, and drying in vacuo (80°C, 0.2 torr) over phosphorus pentaoxide for 48h. The resulting orange solid (0.26 g, 99% yield) had  $\eta_{\text{inh}}=0.24$  in  $\text{CF}_3\text{COOH}$ .

Synthesis of Bromine Complexes. Two preparative methods were used. Small samples of polyester 5 (entree 2, Table IV) and 6 (entree 4, Table II) were

weighed into a watch glass. The samples were subjected to excess bromine vapor (in a closed beaker in the presence of air) for 10 min. The polymers turned black and appeared to soften, somewhat, during the treatment. Analysis of the bromine complex of 5 gave C 47.09, H 3.81, Br 20.71. This corresponds to the empirical formula  $[C_{28}H_{26}O_4S_4Br_{1.99}]_n$  most closely based on the carbon analysis where theory requires C 47.09, H 3.64, Br 22.30.


Analysis of the bromine complex of 6 gave C 48.98, H 2.42, Br 14.47. This corresponds to the empirical formula  $[C_{26}H_{14}O_4S_4Br_{1.49}]_n$  based on the carbon analysis where theory required C 48.98, H 2.22, Br 18.65.

The second method involved heating small amounts of a polyester suspension in a 50%  $CCl_4$  solution of bromine at  $80^\circ$  for 10 min. In this method a substantially larger amount of bromine was incorporated. The resulting polymers were filtered, washed repeatedly with  $CCl_4$ , and dried 24h in vacuo. The bromine complex of 5 obtained in this way analyzed for C 33.32, H 2.70, Br 41.36. This corresponds to the formula  $[C_{28}H_{26}O_4S_4Br_{3.13}]_n$  based on the carbon analysis where theory requires C 33.32, H 2.58, Br 45.01.

Analysis of the bromine complex of 6 prepared in the same way gave C 40.36, H 1.87, Br 26.69. This corresponds to  $[C_{26}H_{14}O_4S_4Br_{3.19}]_n$  based on the carbon analysis where theory requires C 40.36, H 1.83, Br 32.96.


### Results and Discussion

Preparation of Polyesters. 2,6(7)-Bis(p-hydroxyphenyl)tetrathiafulvalene, 4, is unstable in air, quickly turning from an orange color to dark brown. Therefore, its preparation from 2,6(7)-Bis(p-acetoxyphenyl)tetrathiafulvalene (equation 1)<sup>25</sup> and recrystallization from methanol should be carried out under nitrogen and in nitrogenated solvents. After recrystallization from methanol,

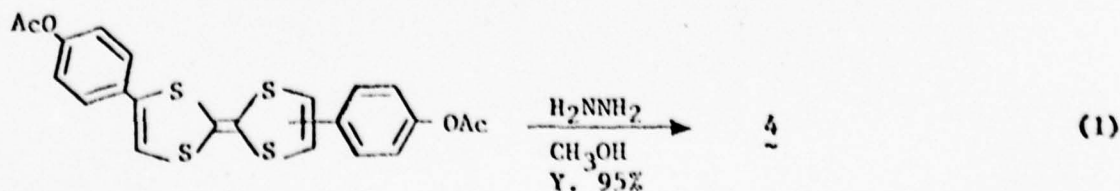



a series of solution polycondensations were carried out at various conditions with sebacyl chloride or terephthaloyl chloride as shown in equation (2). Two general methods were employed. Method A involved the slow, dropwise addition of diacid chloride in solvent to a stirred suspension of diol and base in another solvent at 0°C. Two moles of base were used per mole of diol. Upon completion of the addition of the diacid solution, the polymerization solution was stirred for 12h at 20-25° before the polymer was isolated. Method B involved preparing two solutions of equal volume. One solution contained the diol, 2 equivalents of base, and solvent. The other contained the diacid chloride and solvent. The diacid chloride solution was added all at once to the diol solution with stirring but without cooling. These reactions were stirred for 12h at 20-25°. The polymer was then collected. Method A was used in cases where dual solvents were employed while method B was followed in single solvent reactions. Representative low temperature solution polycondensations and polymer viscosities are given in Table I for 5 (sebacyl polymers) and Table II for 6 (terephthaloyl polymers).

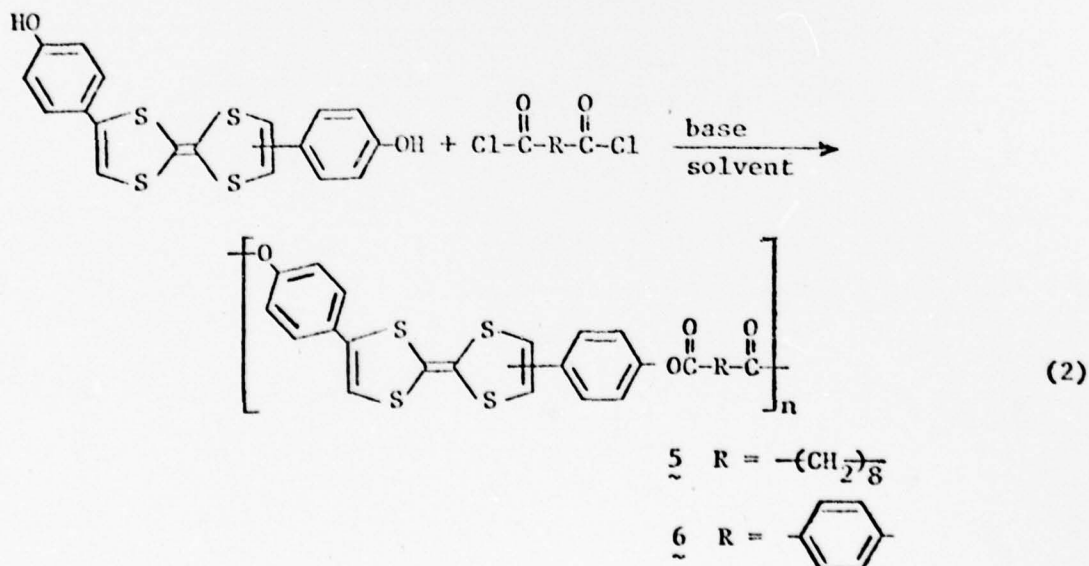

Insert Tables I and II →

Although the polymers were isolated in excellent yields, the molecular

weights remained low over the entire series. In order to determine the influence of base strength in these polymerizations, amines with a wide range of  $pK_a$  values were tested. As shown in Table III, there is no correlation between base strength and the resulting polymer's viscosity despite a change in base strength over a range of six powers of ten.

Insert Table III →

Although the polycondensation proceeds readily at room temperature in solvents such as N,N-dimethylacetamide (DMAC), 1,2-dichloroethane, tetramethylene sulfone (TMS), hexamethylphosphortriamide (HMPA), and chloroform, only low molecular weight polyesters, were obtained. The use of higher temperatures was considered. Thus, additions of diacid chloride to hot diol solutions, in the presence of base, followed by heating at reflux for 12h was tried. These results are summarized in Table IV. Indeed, the molecular weights of 5 did show an increase. However, polycondensations using terephthaloyl chloride at higher temperatures gave 6 with lower molecular weights than were obtained at lower temperature.

Insert Table IV →

The incremental addition method was employed to see if the molecular weights could be increased. Thus, individual polycondensations were carried out with terephthaloyl chloride:4 ratios of 98/100, 99/100, 1/1, 101/100 in tetramethylene sulfone according to method A. The resulting polymers exhibited inherent viscosities of 0.10, 0.16, 0.28, and 0.14 respectively. This demonstrates that the molecular weights were relatively low for reasons other than poorly matched  $M_1/M_2$  ratios.

Characterization. Polyesters 5 and 6 gave elemental analyses in excellent agreement with theory. For example, for polymer 5 (entree 1, Table IV) Calcd. C 60.60, H 4.69, S 23.08; Found C 60.38, H 4.75, S 22.96. For polymer 6 (entree 2, Table II) Calcd: C 60.21, H 2.73, S 24.73; Found: C 60.87, H 2.85, S 24.95. The ir spectra were also in accord with structures 5 and 6. Ester carbonyl absorption

occurred at  $1740\text{--}1730\text{ cm}^{-1}$  and each spectra exhibited bands at 830, 770, and  $720\text{ cm}^{-1}$  which are characteristic of a disubstituted TTF unit.<sup>26</sup>

Polymers 5 and 6 were completely soluble in  $\text{CF}_3\text{COOH}$  at room temperature and soluble in HMPA, DMSO, and DMF on heating. They were only partially soluble in THF and acetone and insoluble in chloroform, methylene chloride, tetrachloroethane, dioxane, diethyl ether, benzene, toluene, and hexane. We were not able to obtain representative gel permeation chromatographic molecular weight determinations since 5 and 6 were only partially soluble in THF.

The glass transition temperature ( $T_g$ ) of polyester 5 was observed at  $140^\circ$  by differential scanning calorimetry (DSC) at a heating rate of  $20^\circ\text{ min}^{-1}$ . This may be compared to the report that homopolymers of 2 do not soften even at  $300^\circ$ .<sup>23</sup> In contrast to 5, the  $T_g$  of polyester 6 could not be detected, presumably because it is expected to be very high. Thermogravimetric analyses (TGA) and differential thermal analyses (DTA) were carried out at  $5^\circ\text{C min}^{-1}$  and  $10^\circ\text{C min}^{-1}$ , respectively on both 5 and 6. Typical thermograms are shown for each polyester in Figures 1 and 2. The DTA curves of 5 exhibited a strong exotherm at about  $280^\circ$  in air which correlated well with TGA studies showing that the initial loss of weight occurred at about this temperature. The decomposition temperature for 10% weight loss was  $\sim 290^\circ\text{C}$  for both 5 and 6 in nitrogen.


The origin of  $280^\circ$  exotherm was found to be due to a reaction of the TTF nucleus. Pure tetrathiafulvalene was studied as a model compound. No thermal decomposition of TTF occurs at its melting point ( $118\text{--}119^\circ$ ). However, at temperatures above  $250^\circ$  it decomposes with gas evolution both in air and under nitrogen. After TTF is raised only briefly to  $280^\circ$  and cooled, it has totally decomposed, according to the ir spectra of the residue. When polyester 5 was heated in sealed tubes at  $280^\circ$  (in air or under nitrogen), the ir bands at 770 and  $720\text{ cm}^{-1}$ , characteristic of the disubstituted TTF nucleus, disappear over a period of  $\sim 5$  minutes. Thus, the TTF nucleus is thermally degraded. The

ester carbonyl bands at  $1740\text{ cm}^{-1}$  remain undiminished.

Attempts to Form TCNQ and DDQ Complexes. Both polyesters 5 and 6 were refluxed in acetonitrile with equimolar amounts of either TCNQ or DDQ under nitrogen for 24h. The product was washed with copious amounts of acetonitrile. The ir spectra of the resulting product was identical to that of 5 or 6 and showed no evidence of the presence of TCNQ or DDQ. Since polyesters 5 and 6 were both soluble in HMPA, hot HMPA solutions of 5 or 6 were reacted with an equivalent of TCNQ (or DDQ). After refluxing for 10-20 min., the solutions were cooled, HMPA was removed in vacuo, and the residue was washed with methanol and dried. Only pure polyester was recovered.

The uv-visible spectra of polyesters 5 and 6 were obtained independently in HMPA, as were the spectra of TCNQ and DDQ. Then HMPA solutions of the polyesters were mixed with TCNQ or DDQ. No evidence of CT complexation was obtained. Both polyesters exhibited strong absorptions at 420 nm, while TCNQ in HMPA has two strong bands at 420 and 500 nm and DDQ absorbs at 405 nm in HMPA. Mixing HMPA solutions of the polyesters with those of TCNQ (or DDQ) gave spectra consistent with simply adding their individual spectra. No low energy CT bands were observed.

Bromine Complexes. Both polyesters 5 and 6 were converted to bromine complexes by exposure to bromine vapor in air at room temperature. By this treatment, 5 was converted to a solid analyzing (see experimental) for  $[\text{C}_{28}\text{H}_{26}\text{O}_4\text{S}_4\text{Br}_{1.99}]_n$  while 6 gave a solid corresponding to  $[\text{C}_{26}\text{H}_{14}\text{O}_4\text{S}_4\text{Br}_{1.49}]_n$ . The infrared spectra of polymers 5 and 6 exhibited absorptions at  $\sim 1600\text{ cm}^{-1}$

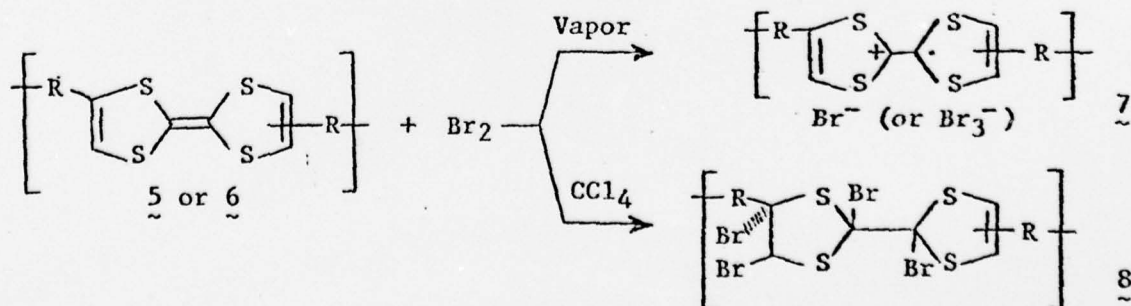



which we attribute to carbon-carbon double bond absorptions from the TTF moiety. Upon treatment with bromine vapor, the intensity of these bands remained undiminished suggesting the complex has a structure such as 7.

The esr spectra were obtained for the  $\text{Br}_3^-$  complexes of polymers 5 and 6. Welcome<sup>19</sup> had previously reported a g value of 2.00789 gauss for the tetrathiafulvalene radical cation in TTF-containing polymers which had been oxidized to  $\text{Br}_3^-$  salts. Using solid samples, the  $\text{Br}_3^-$  salt of 5 exhibited a  $g = 2.0075$  gauss while the  $\text{Br}_3^-$  salt of 6 gave a  $g = 2.0076$  gauss. This provides further evidence for the structure shown in 7.

Polyesters 5 and 6 were also treated with  $\text{CCl}_4$  solutions of bromine to give complexes analyzing for  $[\text{C}_{28}\text{H}_{26}\text{O}_4\text{S}_4\text{Br}_{3.13}]_n$  and  $[\text{C}_{26}\text{H}_{14}\text{O}_4\text{S}_4\text{Br}_{3.19}]_n$ , respectively. In order to see if bromine addition to the double bonds in the TTF nucleus had occurred, the ir spectra were recorded. The absorption at  $\sim 1600 \text{ cm}^{-1}$  found in 5 and 6 was greatly diminished suggesting bromine addition to TTF double bonds as implied by structure 8. Also, carbonyl absorption was found at lower frequencies,  $1680\text{--}1700 \text{ cm}^{-1}$ , suggesting further structural changes in the solid.

Attempts to prepare higher molecular weight condensation polymers from monomer 4 are currently in progress.

### Acknowledgements

Professor Y. Imai, Department of Polymer Chemistry, is thanked for performing the DSC, DTA, and TGA analyses reported here. This work was supported both by the Office of Naval Research, Inorganic Polymers Program and by the University of Alabama.

### References

1. (a) A.F. Garito and A.J. Heeger, Acc. Chem. Res., **7**, 232(1974).  
 (b) E.M. Engler, Chemtech, **6**, 274(1976).  
 (c) J.H. Krieger, Chem. and Eng. News, p. 14-17, July 4(1977).
2. (a) D.B. Tanner, C.S. Jacobson, A.F. Garito, and A.J. Heeger, Phys. Rev. Lett., **32**, 1301(1974).  
 (b) A.A. Bright, A.F. Garito, and A.J. Heeger, Solid State Commun., **13**, 943(1973).  
 (c) L.B. Coleman, M.J. Cohen, D.J. Sandman, F.G. Yamagishi, A.F. Garito, and A.G. Heeger, Solid State Commun., **12**, 1125(1973).  
 (d) F. Wudl, D. Wobschall, and E.J. Hufnagel, J. Am. Chem. Soc., **94**, 671(1972).  
 (e) F. Wudl, A.A. Kruger, and G.A. Thomas, Proc. N.Y. Acad. Sci. USA, **313**(1978).  
 (f) M.L. Kaplan, R.C. Haddon, and F. Wudl, J. Chem. Soc. Chem. Commun., **388**(1977).  
 (g) M. Mizuno, A.F. Garito, and M.P. Cava, J. Chem. Soc. Chem. Commun., **18**(1978).  
 (h) D.C. Green, J. Chem. Soc. Chem. Commun., **161**(1977).  
 (i) Y. Ueno, A. Nakayama, and M. Okawara, J. Am. Chem. Soc., **98**, 7440(1976).
3. J. P. Ferraris, D.O. Cowan, V. Wlatks, and J.H. Perlstein, J. Am. Chem. Soc., **95**, 948(1973).
4. (a) T.E. Phillips, T.J. Kistenmacher, J.P. Ferraris, and D.O. Cowan, J. Chem. Soc. Chem. Commun., **471**(1973).  
 (b) R.C. Wheland, J. Am. Chem. Soc., **99**, 291(1977).
5. (a) E.M. Engler and V.V. Patel, J. Am. Chem. Soc., **96**, 7376(1974).  
 (b) E.M. Engler and V.V. Patel, J. Chem. Soc. Chem. Commun., **671**(1975).  
 (c) E.M. Engler, B.A. Scott, S. Etamad, T. Penney, and V.V. Patel, J. Am. Chem. Soc., **99**, 5909(1977).  
 (d) E.M. Engler, V.V. Patel, J. Chem. Soc. Chem. Commun., **835**(1977).  
 (e) E.M. Engler, V.V. Patel, J.R. Andersen, R.R. Schumaker, and A.A. Fukushima, J. Am. Chem. Soc., **100**, 3769(1978).  
 (f) P. Shu, A.N. Bloch, T.F. Carruthers, and D.O. Cowan, J. Chem. Soc. Chem. Commun., **505**(1977).
6. K. Bechgaard, D.O. Cowan, and A.N. Bloch, J. Chem. Soc. Chem. Commun., **937**(1974).
7. M. Narita and C.U. Pittman, Jr., Synthesis, **6**, 489(1976).



8. G.S. Bajwa, K.D. Berlin, and H.A. Pohl, J. Org. Chem., 41, 145(1976).
9. (a) H.K. Spencer, M.P. Cava, and A.F. Garito, J. Chem. Soc. Chem. Commun., 966(1976).  
(b) N.C. Connelly and M.P. Cava, J. Org. Chem., 43, 369(1978).
10. F. Wudl, A.A. Kruger, M.L. Kaplan, and R.S. Hutton, J. Org. Chem., 42, 768(1977).
11. M.P. Cava and M.V. Lakshmikantham, Ann. N.Y. Acad. Sci., 313, 355(1978).
12. D.C. Green, Ann. N.Y. Acad. Sci., 313, 301(1978).
13. E.P. Goodings, Chem. Soc. Rev., 95(1977).
14. E.P. Goodings, Discuss. Faraday Soc., 51, 157(1971).
15. A.M. Herman, S.P.S. Yen, A. Rembaum, and R.F. Landel, Polym. Lett., 9, 627(1971).
16. C.U. Pittman, Jr. and B. Suryanarayanan, J. Am. Chem. Soc., 96, 7916(1974).
17. C.U. Pittman, Jr., B. Suryanarayanan, and Y. Sasaki, Chapt. 4 in "Inorganic Compounds with Unusual Properties," Edited by R.B. King, Adv. in Chem. Series, Vol. 150, American Chemical Soc. 1976.
18. C.U. Pittman, Jr., Y. Sasaki, and T.K. Mukherjee, Chem. Lett. (Japan), 383(1975).
19. Y. Ueno, Y. Masuyama, and M. Okawara, Chem. Lett. (Japan), 603(1975). For the first report of polymers containing the TTF moiety, see J. R. Welcome, M.S. Thesis, State University of New York at Buffalo (1973).
20. W.R. Hertler, J. Org. Chem., 41, 1412(1976).
21. C.U. Pittman, Jr., M. Narita, and Y.F. Liang, Macromolecules, 9, 360(1976).
22. D.C. Green and R.W. Allen, J. Chem. Soc. Chem. Comm., 832(1978).
23. M.L. Kaplan, R.C. Haddon, F. Wudl, and E.D. Feit, J. Org. Chem., 43(24), 4642(1978).
24. (a) C.U. Pittman, Jr. and M. Narita, Presented at Southeast-Southwest Regional Meeting of the ACS, Memphis, Tenn., Oct. 29-31, 1975, Abstract, no. 139.  
(b) Unpublished studies C.U. Pittman, Jr. and Y.F. Liang.
25. C.U. Pittman, Jr., M. Narita, and Y.F. Liang, J. Org. Chem., 41, 2855(1976).
26. L.R. Melby, H.D. Hartzler, and W.A. Sheppard, J. Org. Chem., 39, 2456(1974).

Table I  
Solution Polycondensations of 2,6(7)-Bis(p-hydroxy-phenyl)tetrathiafulvalene with Sebacyl Chloride at Lower (0-25°) Temperatures.<sup>a</sup>

| Solvent <sup>b</sup>                  | Base          | Polymer  |                             |
|---------------------------------------|---------------|----------|-----------------------------|
|                                       |               | Yield, % | $\eta_{inh}$ . <sup>c</sup> |
| DMAc <sup>d</sup> /1,2-Dichloroethane | pyridine      | 90       | 0.14                        |
| DMAc <sup>d</sup> /1,2-Dichloroethane | triethylamine | 92       | 0.12                        |
| DMAc <sup>d</sup>                     | pyridine      | 81       | 0.12                        |
| DMAc <sup>d</sup>                     | triethylamine | 98       | 0.16                        |
| 1,2-Dichloroethane                    | triethylamine | 89       | 0.14                        |
| TMS <sup>d</sup>                      | pyridine      | 96       | 0.16                        |
| TMS <sup>d</sup>                      | triethylamine | 98       | 0.17                        |
| TMS <sup>d</sup> /1,2-Dichloroethane  | triethylamine | 99       | 0.17                        |
| HMPA <sup>d</sup>                     | pyridine      | 95       | 0.12                        |
| HMPA <sup>d</sup>                     | triethylamine | 95       | 0.13                        |
| HMPA <sup>d</sup> /1,2-Dichloroethane | triethylamine | 96       | 0.14                        |
| Chloroform                            | triethylamine | 97       | 0.18                        |

<sup>a</sup>All polycondensations were carried out using 1 mmol of each monomer and 2 mmol of base in 2 ml of solvent at 20-25° for 12h. <sup>b</sup>Method A was employed in reactions using mixed solvents. Method B was used wherever a single solvent was used. <sup>c</sup>Measured at a concentration of 0.5g/dl in CF<sub>3</sub>COOH at 30°. <sup>d</sup>DMAc=dimethylacetamide, TMS=tetramethylene sulfone, HMPA=hexamethylphosphortriamide.

Table II  
Solution Polycondensations of 2,6(7)-Bis(p-hydroxy-phenyl)tetrathiafulvalene with Terephthaloyl Chloride at Lower (0-25°) Temperatures.<sup>a</sup>

| Solvent           | Base          | Polymer  |               |
|-------------------|---------------|----------|---------------|
|                   |               | Yield, % | $\eta_{inh.}$ |
| CHCl <sub>3</sub> | pyridine      | 96       | 0.16          |
| CHCl <sub>3</sub> | triethylamine | 98       | 0.25          |
| TMS <sup>b</sup>  | pyridine      | 96       | 0.17          |
| TMS <sup>b</sup>  | triethylamine | 98       | 0.28          |
| DMAc <sup>b</sup> | triethylamine | 98       | 0.25          |

<sup>a</sup>All polycondensation were conducted by Method B and employed 1 mmol. of each monomer and 2 mmol. of base in 2 ml. of solvent at 20-25° for 12h.

<sup>b</sup>TMS=tetramethylenesulfone, DMAc=dimethylacetamide.

Table III  
Effect of the pK<sub>a</sub> of Added Base on Polymer Molecular Weight in Polycondensations of 2,6(7)-Bis(p-hydroxy-phenyl)tetrathiafulvalene with Sebacyl Chloride Using Method A in Chloroform.

| Base              | (pK <sub>a</sub> ) | Polymer  |               |
|-------------------|--------------------|----------|---------------|
|                   |                    | Yield, % | $\eta_{inh.}$ |
| Triethylamine     | (10.75)            | 97       | 0.18          |
| N-Ethylmorpholine | (7.67)             | 96       | 0.14          |
| 2,6-Lutidine      | (6.60)             | 99       | 0.20          |
| 2-Picoline        | (5.94)             | 98       | 0.16          |
| Pyridine          | (5.22)             | 90       | 0.14          |
| Isoquinoline      | (4.81)             | 98       | 0.12          |

Table IV  
Higher Temperature Solution Polycondensations  
of 2,6(7)-Bis(p-hydroxyphenyl)tetrathiafulvalene  
with Sebacyl and Terephthaloyl Chlorides.<sup>a</sup>

| Polymer | Solvent  | Base          | Yield, % | $\eta_{inh.}$ |
|---------|----------|---------------|----------|---------------|
| 5       | p-xylene | pyridine      | 100      | 0.24          |
| 5       | p-xylene | triethylamine | 98       | 0.22          |
| 6       | p-xylene | triethylamine | 99       | 0.11          |
| 6       | p-xylene | pyridine      | 94       | 0.07          |
| 6       | toluene  | triethylamine | 90       | 0.16          |
| 6       | toluene  | pyridine      | 90       | 0.15          |

<sup>a</sup>Each polycondensation was carried out at reflux for 12h using 1 mmol. of each monomer and 2 mmol. of base in 2 ml. of solvent.



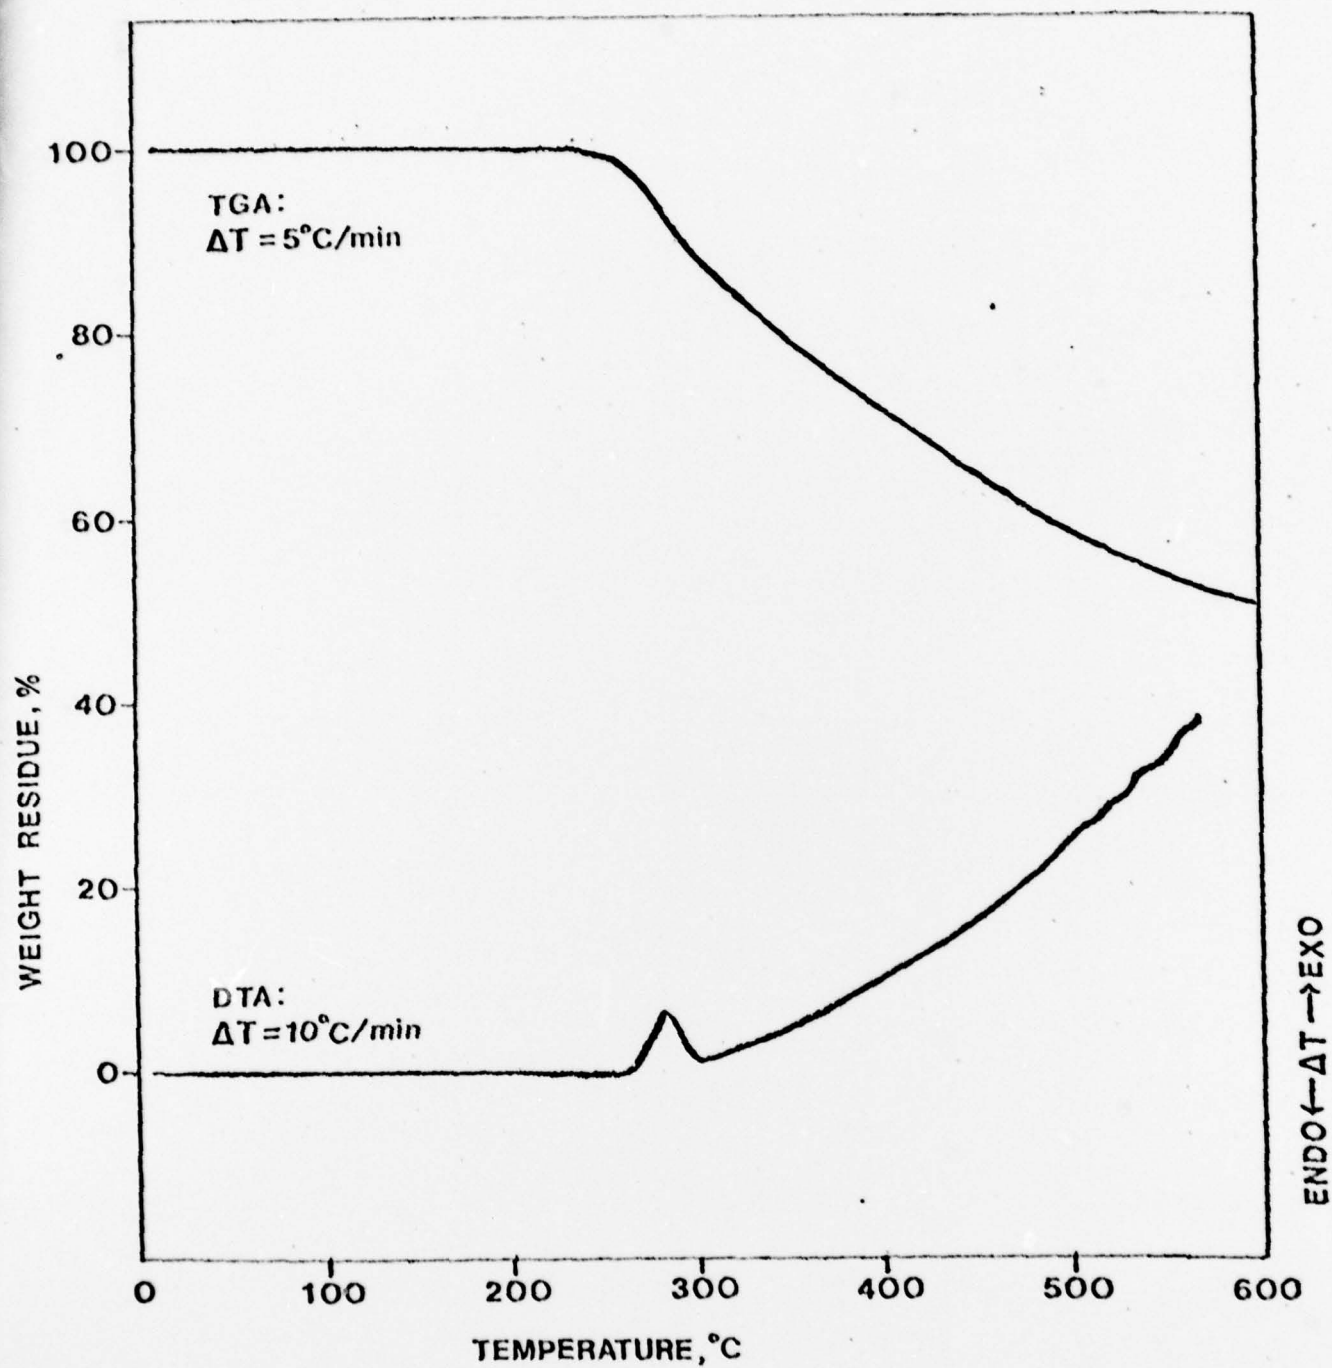


Fig.1. DTA and TGA curves of polyester 5.

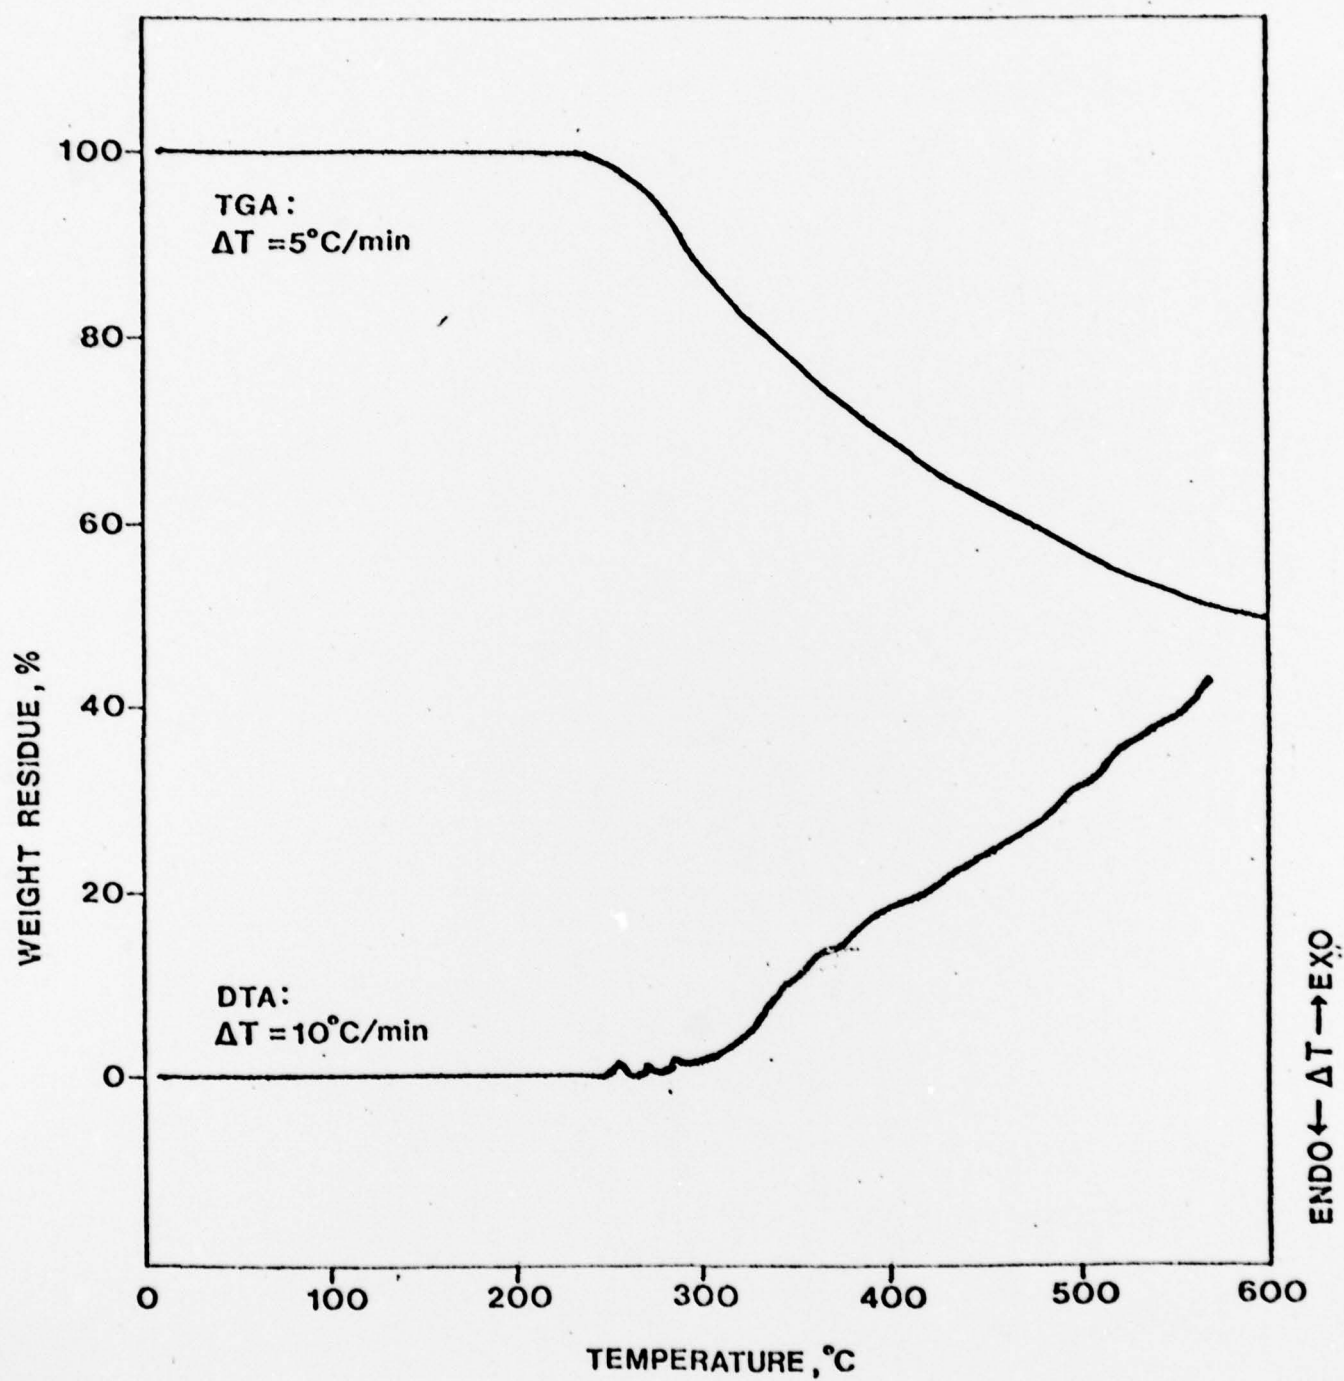


Fig. 2. DTA and TGA curves of polyester 6 .



472:GAN:716:tam  
78u472-608

TECHNICAL REPORT DISTRIBUTION LIST, GEN

|  | <u>No.</u><br><u>Copies</u> |  | <u>No.</u><br><u>Copies</u> |
|--|-----------------------------|--|-----------------------------|
| Office of Naval Research<br>800 North Quincy Street<br>Arlington, Virginia 22217<br>Attn: Code 472                           | 2                           | Defense Documentation Center<br>Building 5, Cameron Station<br>Alexandria, Virginia 22314  | 12                          |
| ONR Branch Office<br>536 S. Clark Street<br>Chicago, Illinois 60605<br>Attn: Dr. George Sandoz                               | 1                           | U.S. Army Research Office<br>P.O. Box 1211<br>Research Triangle Park, N.C. 27709<br>Attn: CRD-AA-IP                                | 1                           |
| ONR Branch Office<br>715 Broadway<br>New York, New York 10003<br>Attn: Scientific Dept.                                      | 1                           | Naval Ocean Systems Center<br>San Diego, California 92152<br>Attn: Mr. Joe McCartney   | 1                           |
| ONR Branch Office<br>1030 East Green Street<br>Pasadena, California 91106<br>Attn: Dr. R. J. Marcus                          | 1                           | Naval Weapons Center<br>China Lake, California 93555<br>Attn: Dr. A. B. Amster<br>Chemistry Division                               | 1                           |
| ONR Area Office<br>One Hallidie Plaza, Suite 601<br>San Francisco, California 94102<br>Attn: Dr. P. A. Miller                | 1                           | Naval Civil Engineering Laboratory<br>Port Hueneme, California 93401<br>Attn: Dr. R. W. Drisko                                     | 1                           |
| ONR Branch Office<br>Building 114, Section D<br>666 Summer Street<br>Boston, Massachusetts 02210<br>Attn: Dr. L. H. Peebles  | 1                           | Professor K. E. Woehler<br>Department of Physics & Chemistry<br>Naval Postgraduate School<br>Monterey, California 93940            | 1                           |
| Director, Naval Research Laboratory<br>Washington, D.C. 20390<br>Attn: Code 6100   | 1                           | Dr. A. L. Slafkosky<br>Scientific Advisor<br>Commandant of the Marine Corps<br>(Code RD-1)<br>Washington, D.C. 20380               | 1                           |
| The Assistant Secretary<br>of the Navy (R,E&S)<br>Department of the Navy<br>Room 4E736, Pentagon<br>Washington, D.C. 20350   | 1                           | Office of Naval Research<br>800 N. Quincy Street<br>Arlington, Virginia 22217<br>Attn: Dr. Richard S. Miller                       | 1                           |
| Commander, Naval Air Systems Command<br>Department of the Navy<br>Washington, D.C. 20360<br>Attn: Code 310C (H. Rosenwasser) | 1                           | Naval Ship Research and Development<br>Center<br>Annapolis, Maryland 21401<br>Attn: Dr. G. Bosmajian<br>Applied Chemistry Division | 1                           |
|  |                             | Naval Ocean Systems Center<br>San Diego, California 91232<br>Attn: Dr. S. Yamamoto, Marine<br>Sciences Division                    | 1                           |

Encl 1

TECHNICAL REPORT DISTRIBUTION LIST, 356B

|  | <u>No.</u><br><u>Copies</u> |   | <u>No.</u><br><u>Copies</u> |
|--|-----------------------------|---|-----------------------------|
| Dr. T. C. Williams<br>Union Carbide Corporation<br>Chemical and Plastics<br>Tarrytown Technical Center<br>Tarrytown, New York    | 1                           | Douglas Aircraft Company<br>3855 Lakewood Boulevard<br>Long Beach, California 90846<br>Attn: Technical Library<br>CI 290/36-84<br>AUTO-Sutton | 1                           |
| Dr. R. Soulen<br>Contract Research Department<br>Pennwalt Corporation<br>900 First Avenue<br>King of Prussia, Pennsylvania 19406 | 1                           | NASA-Lewis Research Center<br>21000 Brookpark Road<br>Cleveland, Ohio 44135<br>Attn: Dr. T. T. Serafini, MS 49-1                              | 1                           |
| Dr. A. G. MacDiarmid<br>University of Pennsylvania<br>Department of Chemistry<br>Philadelphia, Pennsylvania 19174                | 1                           | Dr. J. Griffith<br>Naval Research Laboratory<br>Chemistry Section, Code 6120<br>Washington, D.C. 20375  | 1                           |
| Dr. C. Pittman<br>University of Alabama<br>Department of Chemistry<br>University, Alabama 35486                                  | 1                           | Dr. G. Goodman<br>Globe-Union Incorporated<br>5757 North Green Bay Avenue<br>Milwaukee, Wisconsin 53201                                       | 1                           |
| Dr. H. Allcock<br>Pennsylvania State University<br>Department of Chemistry<br>University Park, Pennsylvania 16802                | 1                           | Dr. E. Fischer, Code 2853<br>Naval Ship Research and<br>Development Center<br>Annapolis Division<br>Annapolis, Maryland 21402                 | 1                           |
| Dr. M. Kenney<br>Case-Western University<br>Department of Chemistry<br>Cleveland, Ohio 44106                                     | 1                           | Dr. Martin H. Kaufman, Head<br>Materials Research Branch (Code 4542)<br>Naval Weapons Center<br>China Lake, California 93555                  | 1                           |
| Dr. R. Lenz<br>University of Massachusetts<br>Department of Chemistry<br>Amherst, Massachusetts 01002                            | 1                           | Dr. J. Magill<br>University of Pittsburg<br>Metallurgical and Materials<br>Engineering<br>Pittsburg, Pennsylvania 22230                       | 1                           |
| Dr. M. David Curtis<br>University of Michigan<br>Department of Chemistry<br>Ann Arbor, Michigan 48105                            | 1                           | Dr. C. Allen<br>University of Vermont<br>Department of Chemistry<br>Burlington, Vermont 05401   | 1                           |
| Dr. M. Good<br>University of New Orleans<br>Department of Chemistry<br>Lakefront<br>New Orleans, Louisiana 70122                 | 1                           | Dr. D. Bergbreiter<br>Texas A&M University<br>Department of Chemistry<br>College Station, Texas 77843   | 1                           |

472:GAN:716:tam  
78u472-608

TECHNICAL REPORT DISTRIBUTION LIST, 356B

No.  
Copies

Professor R. Drago  
Department of Chemistry  
University of Illinois  
Urbana, Illinois 61801

1

Dr. F. Brinkman  
Chemical Stability & Corrosion  
Division  
Department of Commerce  
National Bureau of Standards  
Washington, D.C. 20234

1